



Research Paper

PREPARATION AND PROPERTY EVALUATION OF ALUMINIUM-SILICA COMPOSITES BY CASTING ROUTE

Mallikarjuna G B^{1*}, K V Sreenivas Rao¹ and R H Jayaprakash¹

*Corresponding Author: **Mallikarjuna G B**, ✉ mallikarjun.gb06@gmail.com

Metal Matrix Composites (MMC's) have been developed to meet the demand for lighter materials with high specific strength, stiffness and wear resistance. Among Metal matrix composites particulate reinforced aluminium matrix composites are attractive due to significant improvements in mechanical and physical properties like such as superior strength to weight ratio, good ductility, high strength and high modulus, low thermal expansion coefficient, excellent wear resistance, excellent corrosion resistance, high temperature creep resistance and better fatigue strength. Aluminium based MMC's find wide applications in aerospace, automobiles and marine sectors, etc. The mechanical properties of aluminium matrix composites are strongly dependent on microstructural parameters like shape, size, volume fraction and distribution of reinforcement particles which have to be carefully chosen. Therefore, judicious selection of the variables is important to optimize the properties of the composites. In this present work, metal matrix composites with Al alloy LM13 as matrix and silicon dioxide particulates were produced with varying amount of 3 to 12 wt% in steps of 3 for particle size 106 μm and were fabricated by stir casting process. Above prepared composites are subjected to the mechanical testing as per the ASTM standards. The investigation reveals that there is a significant improvement in the mechanical properties of the composite. The tensile strength and hardness were found to increase with the increase in the wt% of SiO_2 reinforcement.

Keywords: Al alloy LM13, Silica, Stir casting

INTRODUCTION

Industrial technology is growing at a very rapid rate and consequently there is an increasing demand and need for new materials.

Particulate reinforced composites constitute a large portion of these new advanced materials. The choice of the processing method depends on the property

¹ Siddaganga Institute of Technology, Tumkur, India.

requirements, cost factor consideration and future applications prospects (Hamouda *et al.*, 2007).

Incorporation of hard second phase particles in the alloy matrices to produce MMCs has also been reported to be more beneficial and economical due to its high specific strength and corrosion resistance properties (Thoguluva, 2009).

Aluminium Alloy Composites (AACs) are becoming potential engineering materials offering excellent combination of properties such as high specific strength, high specific stiffness, electrical and thermal conductivities, low coefficient of thermal expansion and wear resistance (Das, 2004). A good combination of high strength and ductility of the Aluminum based metal matrix composites (MMCs) have introduced the material to a wide area of possible advanced applications (Wahab *et al.*, 2009). For instances, reinforcing aluminium metal with silica particulate yields a material that displays combination of physical and mechanical properties of both the metal matrix and the silica. The demand for structural materials to be cost effective and also to provide high performance has resulted in continuous attempts to develop composites as serious competitors to the traditional engineering alloys (Zuhailawati *et al.*, 2007). Accordingly, the objective of the present study was to investigate the mechanical properties of aluminium matrix composites reinforced with low-cost silica sand, which is attained from mines. Particular emphasis was placed to study the effect of presence of silica reinforcing particulates on the microstructural variation in the metallic material and to correlate the particulate's associated microstructural

variation in the metallic material with the hardness and modulus of fracture of the metallic matrix.

Al based MMCs refer to the class of light weight high performance Al centric material systems. The reinforcement in Al MMCs could be in the form of continuous/discontinuous fibres, whiskers or particulates in volume or weight fraction ranging from 15% up to 70%. Properties of Al based MMCs can be tailored to the demands of different industrial applications by suitable combinations of matrix, reinforcement and processing route (Joel, 2009). Strength and hardness increase with increase in dispersoid content and this may be possibly because of the occurrence of a more uniform distribution of SiO₂ particles within the matrix (Babu *et al.*, 2010).

EXPERIMENT

The materials used in this work are aluminium LM13 alloy for the matrix and SiO₂ of 106 µm as particulates with different percentages (in wt% 3, 6, 9 and 12) based on the variation in weight. The tensile test specimens of SiO₂ particulate reinforced LM13 alloy composites used here is prepared according to ASTM E8M standards. The toughness and formability of Aluminum –12% silicon alloy can be combined with the strength of quartz particles. Cast iron permanent mould is used for processing composite castings. The details of the LM13 alloy composition is shown in Table 1. Quartz is a hard mineral and provides excellent hardness on incorporation into the soft lead-alloy, thereby making it better suited for applications where hardness is desirable. The mechanical, thermal and electrical properties of LM13 are shown in the Table 2.

Table 1: Chemical Composition of LM13, wt%

Cu	Zn	Mg	Si	Ni	Fe
0.7	0.5	1.5	12	1.5	1.0
Mn	Pb	Sn	Ti	Al	
0.5	0.1	0.1	0.2	Bal	

Table 2: Mechanical, Thermal and Electrical Properties of LM13

Physical Properties	Values
Density (g/cm ³)	2.7
Mechanical Properties	Values
Tensile strength (MPa)	170-200
0.2% proof stress (MPa)	160-190
Elongation %	0.5
Hardness (VHN)	130
Thermal Properties	Values
Coefficient of thermal expansion (°C at 20-100 °C)	0.000019
Coefficient of thermal expansion (°C at 20-300 °C)	0.000021
Thermal conductivity (cal/cm ² /cm/°C at 25 °C)	0.28
Melting point (°C)	695
Electrical Properties	Values
Electrical conductivity (% copper standard at 25 °C)	29

Table 3: Properties of Reinforcement Silica

Properties	Values
Tensile strength	25 N/mm ²
Melting point	1830 °C
Boiling point	2230 °C
Density	2.65 gm/cm ³
Thermal conductivity	1.3 W/m-k
Compressive strength	2070 N/mm ²
Poisson's ratio	0.17
Modulus of elasticity	70 GPa
Thermal shock resistance	Excellent

LM13 alloy is actually a eutectic alloy having the lowest melting point that can be seen from the Al-Si phase diagram. The main composition of LM13 is about 85.95% of aluminum, 12% to 13% of silicon. The properties of pure SiO₂ are in the Table 3.

Test Procedure

Microscopic examination of the MMCs was executed by means of optical microscopy. Various etchant were tried but dilute Kellers etchant proved to be the best and was therefore used. Hardness tests were performed with a Vickers micro Hardness (Zwick/Roell ZHV, German make) testing machine on the polished specimens used for microstructural analysis. The specifications dimension, and shape of the specimen used are shown in the Figure 1 and a clear explanation in given below. SiO₂-particulate reinforced LM13 alloy composite cast test specimens are processed by stir casting process. Different wt% percentage of SiO₂ particulates are added to produce the cast test samples. The photograph of the tensile test specimens before and after testing is shown in the Figures 2 and 3. A 150 KN servo hydraulic UTM is used to conduct the tensile tests. The test samples are subjected to a

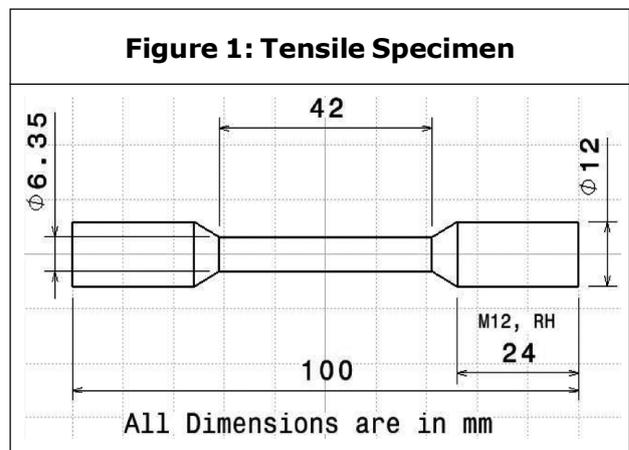


Figure 2: Tensile Specimens Before Test



Figure 3: Tensile Specimens After Testing



tensile load and the mechanical properties are determined. Hence, the tensile strength, and young's modulus values are calculated

RESULTS AND DISCUSSION

Microstructure

The microstructure of Al-Si (LM13) alloy, in as cast condition, shows the dendrites of aluminum and eutectic silicon in the

interdendritic regions and around the dendrites. The micrograph of LM13 with 3 to 12 wt.% Silica composite, in as cast condition, shows uniform distribution of Silica particles in Aluminum matrix. Figure 4 shows the microstructural observation of prepared composites.

Figure 4: Optical Micrograph of Al Alloy LM13-Silica of 106 μm at Resolution 100X


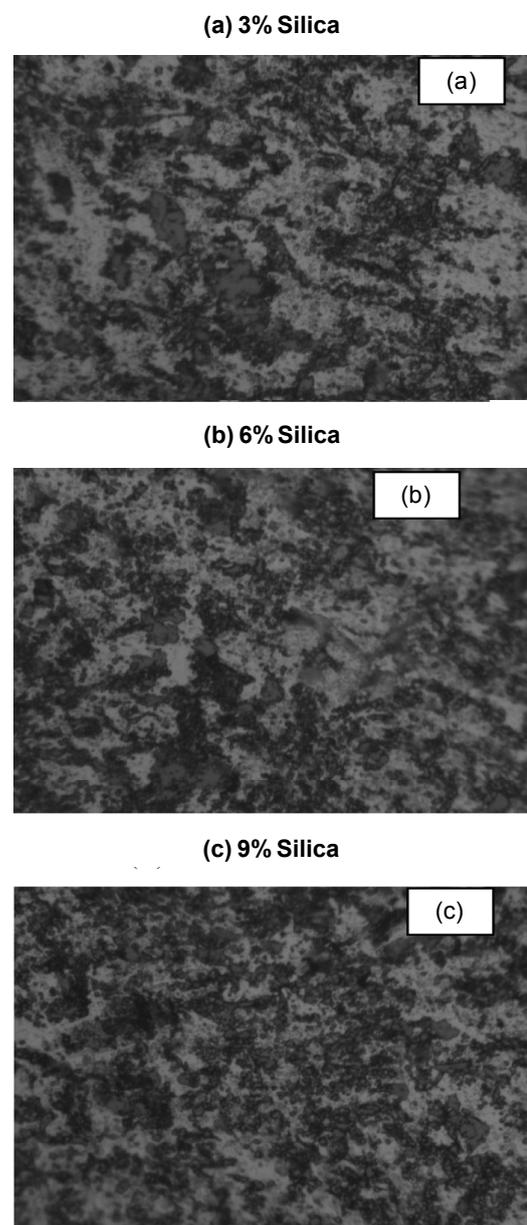



Figure 4 (Cont.)

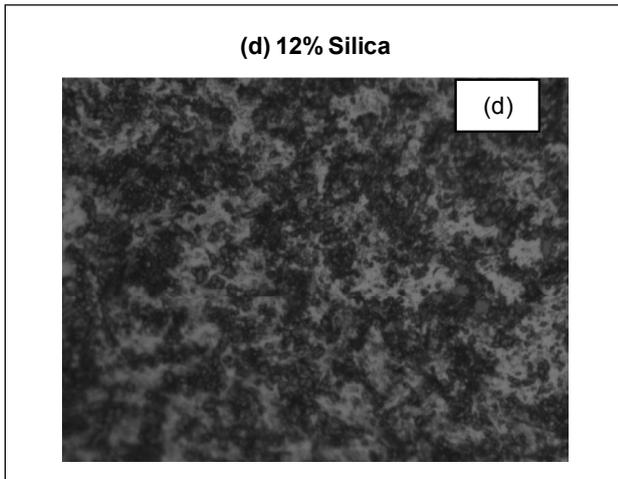

Tensile Strength

The value of tensile strength and % of SiO₂ is shown in the Table 4. The Figure 5 shows variation in tensile strength of Al-SiO₂ particulate composites for 106 μ particle size. The tensile strength increased with increased weight percentage of SiO₂ up to 9 and decreased in 12 weight percentage. Because the increase in the percent of closed pores with

Weight Percentage of Silica	Tensile Strength in MPa
3	192.823
6	197.870
9	209.894
12	114.129

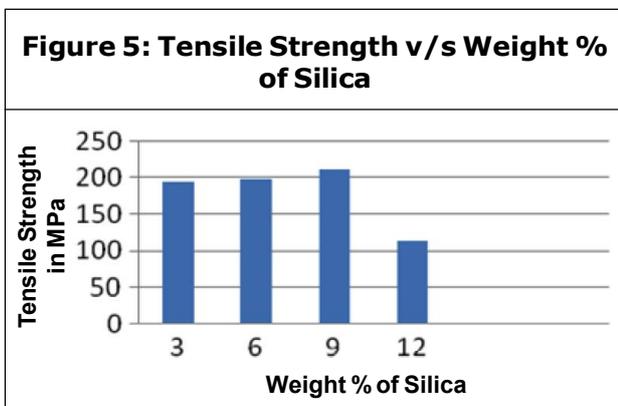


increasing SiO₂ particulate content would create more sites for crack initiation and hence lower down the load bearing capacity of the composite. Besides if the number of contacts between SiO₂ particulate increases, then the particles is no longer isolated by the ductile aluminium alloy matrix.

Hardness

Hardness tests were performed on composites to know the effect of silica in matrix material. The polished specimens were tested using Vickers micro hardness testing system. A load of 50 grams for a period of 10 seconds was applied on specimens. The hardness was determined by recording the diagonal lengths of indentation produced. The test was carried out at six different locations and the average value was taken as the hardness of the composite specimens. Table 5 shows the results of micro hardness test on composite containing different wt% of silica in it. From the Figure 6 it is evident that the hardness of the composite material is much higher than that of its parent metal. It is also shown that the hardness of the composite material increases with wt% of silica content. This may be because of addition of silica makes the ductile Al alloy into more brittle in nature with increase in the silica content. And also the dispersion of silica particles enhances the hardness, as particles are harder than Al alloy, and render

Weight Percentage of Silica	Hardness (VHN)
3	141
6	156
9	171
12	148

their inherent property of hardness to soft matrix.

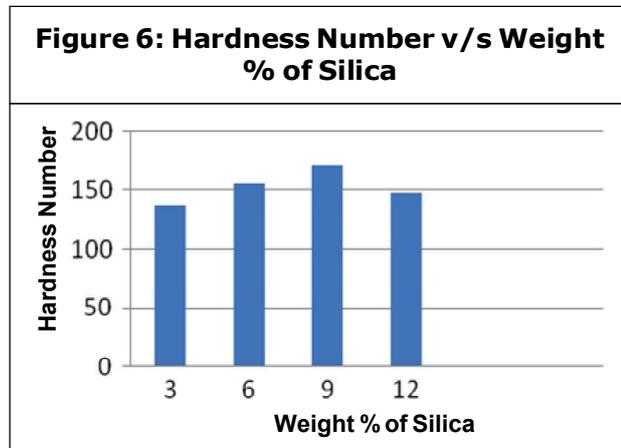

CONCLUSION

The significant conclusions of the studies on Al alloy LM13-Silica metal matrix composites are as follows.

- Liquid metallurgy techniques were successfully adopted in the preparation of Al alloy LM13-Silica composites containing the reinforcement up to 12 wt%.
- The microstructural studies revealed the uniform distribution of the particles in the matrix system.
- Strength is increases up to weight percentage of 9 of silica for micron size of 106 μm , after that decreases.
- Microhardness of the composites found increases with increased weight percentage of 9 of silica for micron sizes of 106 μm , after that decreases.
- From the studies it can be concluded that Al alloy LM13-Silica exhibits superior mechanical properties. 🌀

ACKNOWLEDGMENT

I would like to thank Mr K V Sreenivasrao, Professor and Mr R H Jayaprakash, Associate

Prof. Department of Mechanical Engineering, SIT Tumkur to his continuous support and guidance throughout my project work.

REFERENCES

1. Babu Rao J, Venkata Rao D and Bhargava N R M R (2010), "Development of Light Weight ALFA Composites", *International Journal of Engineering, Science and Technology*, Vol. 2, No. 11, pp. 50-59.
2. Das S (August 2004), "Development of Aluminium alloy Composites for Engineering Applications", Vol. 57, No. 4, pp. 325-334.
3. Hamouda A M S, Sulaiman S, Vijayaram T R, Sayuti M and Ahmad M H M (December 2007), "Processing and Characterisation of Particulate Reinforced Aluminium Silicon Matrix Composite", *Journal of Achievements in Materials and Manufacturing Engineering*, Vol. 25, No. 2.
4. Joel Hemanth (2009), "Quartz (SiO_2) Reinforced Chilled Metal Matrix Composite (CMMC) for Automotive Applications", *Materials and Design*, Vol. 30, pp. 323-329.
5. Thoguluva Raghavan Vijayaram (March 2009), "Foundry Metallurgy of Silicon Dioxide Particulate-Reinforced LM6 Alloy Matrix Composites, Studies on Tensile Properties, and Fractography", *Indian Foundry Journal*, Vol. 55, No. 3.
6. Wahab M N, Daud A R and Ghazali M J (2009), "Preparation and

Characterization of Stir Cast-Aluminum Nitride Reinforced Aluminum Metal Matrix Composites”, *International Journal of Mechanical and Materials Engineering (IJMME)*, Vol. 4, No. 2, pp. 115-117.

7. Zuhailawati H, Samayamutthirian P and Mohd Haizu C H (2007), “Fabrication of Low Cost of Aluminium Matrix Composite Reinforced with Silica Sand”, *Journal of Physical Science*, Vol. 18, No. 1, pp. 47-55.