

# Physico-Mechanical and Tribological Properties of Glass Fiber based Epoxy Composites

Vijay B R and Dr. Srikantappa A S

Cauvery Institute of Technology, India

Email: vijay.akshath@gmail.com; srikantappaarakere@gmail.com

**Abstract**—Polymeric materials reinforced with synthetic fibers like glass, carbon, and aramid provide advantage of high stiffness and strength to weight ratio as compared to conventional materials like wood, concrete etc. In the light of these the present experimental study aims at learning the physico-mechanical and tribological properties of glass epoxy composite filled with a filler of MoS<sub>2</sub>. Hand layout technique is employed for preparing the samples, with varying weight fraction of bi-directional glass fiber. The ratio of filler is varied between 0 to 6 wt.-%. Specimens were cut from the fabricated laminate according to the ASTM standards for different experiments. The systematic experimentation leads to determination of significant process parameters and material variables that predominantly influence the wear rate. It has been found that wear rate increases with increasing abrading distance and for 4% filler optimized wear strength were achieved. Mechanical properties of composites are increases with increase of filler. The mechanical and wear behaviour of filled composites is more superior then unfilled composites.

**Index Terms**—glass fiber, mechanical properties, MoS<sub>2</sub> filler, tribological properties.

## I. INTRODUCTION

Bi-directional glass fiber reinforced polymer composites is widely used in many industrial applications due to several advantages such as low weight, ease of processing, price and noise suspension. The performance of the composites can be further improved by adding particulate filler to them. The “filler” play an important role for the improvement in performance of polymer composites. Filler materials are generally used to reduce the cost of material and to improve mechanical properties to some extent and in some cases to improve its process ability. Besides this, it is also used to increase the properties like reduce shrinkage, hardness and wear resistance [1][ 2]. Fibre reinforced polymer composites containing different filler are used in many application in which tribological and mechanical properties are critical issues [3][4][5]. Also a full understanding of the effects of all system variables on the wear rate is necessary in order to undertake appropriate steps in the design of machine or structural component and in the choice of materials to reduce/control wear [6].

Many researchers are worked on glass/carbon fibers reinforced epoxy composites and they find optimized values with the addition of fillers [7][8][9].

Most of the researchers are used Sic and graphite as filler due to his unique properties and optimized results with the addition of fillers [10][11][12].

Although a great deal of work has been reported in the literature which discuss the mechanical and wear behaviour of fiber reinforced polymer composites with and without filler, however a very less work has been done on effect of MoS<sub>2</sub> filler on mechanical and wear behaviour of bi-directional glass fiber reinforced epoxy composites. Against this background, In the present investigation, Composites samples are made by using simple hand-lay-up technique with varying weight fraction of bi-directional glass fiber and MoS<sub>2</sub> filler. The effects of fiber loading and filler on the tribological and mechanical behaviour of epoxy composites are studied.

## II. SPECIMEN AND EXPERIMENTAL SETUP

The fabrication of the various composite materials is carried out through hand layup technique. The composite fabrication consist of three steps: (a) mixing of epoxy resin and filler using a mechanical stirrer, (b) mixing of the curing agent with the filled epoxy resin, and (c) fabrication of composites. Resin and hardener (HY 951) mixed in a ratio of 10:1 by weight as recommended. MoS<sub>2</sub> powder of average size 100-200 µm mixed with epoxy resin by stirring at room temperature and poured in to the wooden mould of dimension (210X210X40) mm<sup>3</sup>. The composite sample of three different compositions samples i.e. Sample EG-1 (60% glass fiber + 40% epoxy), sample EG-2 (60% glass fiber + 38% Epoxy + 2% Filler), EG-3 (60% glass fiber+ 36% Epoxy + 4% Filler). The cast of each composite is cured under a load of about 20 kg for 24 hours before it is removed from the mould. Then this cast material is allowed for post curing in the air for another 24 hours after removing out of the mould. Test specimen of 3mm thickness and 50mm length are cut from composite sheets for airjet erosion test. Test specimen of 76 mm length and 25.4 mm width are cut from composite sheets for wear test. After fabrication the test specimens were subjected to various mechanical tests as per ASTM standard. Generally flat specimens are used for tension test. A uniaxial load is applied through both the ends. The dimension of the samples for the test is 150

mm X 10 mm and thickness of approximately 3mm. The test is performed in the universal testing machine and the test is repeated three times for each sample to obtain the mean value of tensile strength. The abrasion testing of composite specimens is performed on a standard abrasion test rig (supplied by DUCOM) as per ASTM G-65 standard and air jet erosion test as per ASTM G76. The material losses from the composite surface are measured by using precision electronic balance.

### III. DISCUSSION

#### A. Density

The theoretical and measured densities along with the corresponding volume fraction of voids were presented in Table 1. It was clear from the Table 1 that the volume fraction of voids was negligible, and this was due to the absence of particulate fillers. With the addition of filler materials more voids were found in the composites. As the filler content changes from composites to composites the volume fraction of voids was also found to be changed.

TABLE I. THEORETICAL AND MEASURED DENSITY VALUES OF THE COMPOSITES WITH VOLUME FRACTION OF VOIDS

Composites	Measured Density (g/cc)	Theoretical Density(g/cc)	Volume fraction of Voids
EG-1	1.52	1.54	0.902
EG -2	1.65	1.72	4.126
EG-3	1.65	1.71	4.817

Density of a composite depends on the relative proportion of matrix and reinforcing materials and this was one of the most important factors determining the properties of the composites. The voids significantly affect some of the mechanical properties and even the performance of composites in the place of use. Higher void contents usually mean lower fatigue resistance, greater susceptibility to water penetration and weathering.

#### B. Tensile Properties

Tensile test was conducted on the Hounstall's universal testing machine in accordance with ASTM D638. Table 2 shows the details of the same.

TABLE II. TENSILE TEST RESULTS

Sl.No	Specimen	Max. Load(N)	Tensile stress at maximum load (N/mm <sup>2</sup> )	Extension at max load (mm)	Extension at break (mm)	Tensile strain at break (%)	Modulus (N/mm <sup>2</sup> )
1	GE-1	16377.3	418.08	4.23	4.27	8.53	7416.49
2	GE-2	18430.75	455.37	4.86	4.88	9.76	6582.03
3	GE-3	18986.3	476.72	4.91	4.92	9.84	5831.87

In this study, percentage of elongation, tensile strength and tensile modulus at fracture of unfilled and MoS<sub>2</sub>

filled glass fiber reinforced epoxy composites are plotted as a function of MoS<sub>2</sub> filler and the same is shown in Fig.1, 2 and 3. Fig.1 shows the percentage elongation of glass fiber reinforced epoxy composite with and without MoS<sub>2</sub> filler. It is observed that, the glass fiber reinforced epoxy composites with 4% MoS<sub>2</sub> filler has highest elongation of 4.92mm and glass fiber reinforced epoxy composite without MoS<sub>2</sub> filler the elongation is 4.27. Fig.2 shows a linear increase in the tensile strength as the percentage of MoS<sub>2</sub> increased. The tensile strength of composite without filler and with 2% and 4% of the MoS<sub>2</sub> content has been increased from 418.08 Mpa to 476.72 Mpa. The tensile modulus from fig.3 shows that, decrease in modulus as the filler content in the composite is increased. These observations suggest overall improvement in tensile properties with the addition of MoS<sub>2</sub> filler.

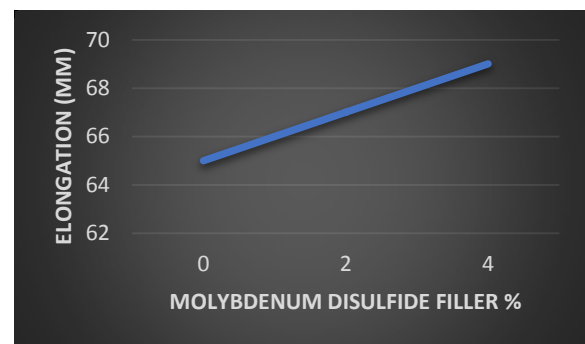


Figure 1. Percentage elongation as a function of MoS<sub>2</sub> filler content.

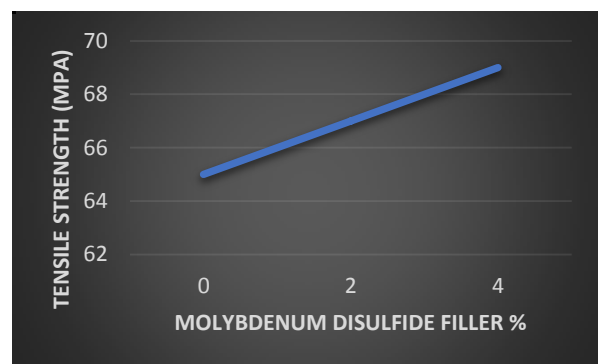


Figure 2. Tensile strength as a function of MoS<sub>2</sub> filler content.

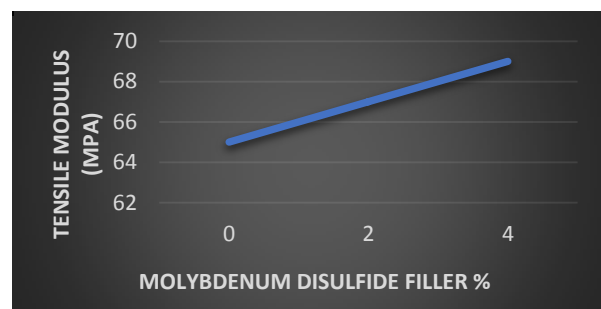




Figure 3. Tensile Modulus as a function of MoS<sub>2</sub> filler content.

### C. Flexural Properties

TABLE III. FLEXURAL TEST RESULTS

Sl.No	Specimen	Support Span (mm)	Max. Load(N)	Max stress (N/mm <sup>2</sup> )	Flex modulus(N/mm <sup>2</sup> )
1	GE-1	50	679.54	466.64	37757.46
2	GE-2	50	1022.33	583.06	41408.63
3	GE-3	50	654.32	398.76	33979.37

Fig.4 and 5 shows the variation of flexural strength and modulus as a function of MoS<sub>2</sub> filler. Glass fiber reinforced epoxy composite with 4% MoS<sub>2</sub> additives showed the least flexural strength and modulus. Whereas the one with 2% of MoS<sub>2</sub> filler indicated the maximum value suggesting that if flexural properties are important in any application, one should use minimum filler content. (Table 3)

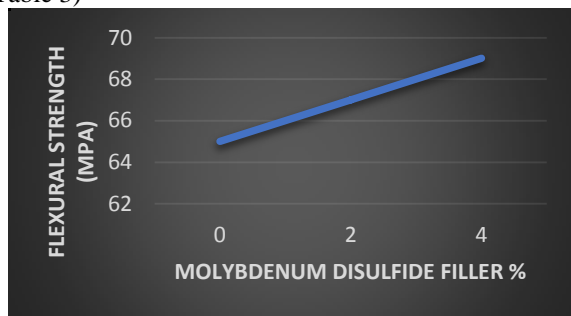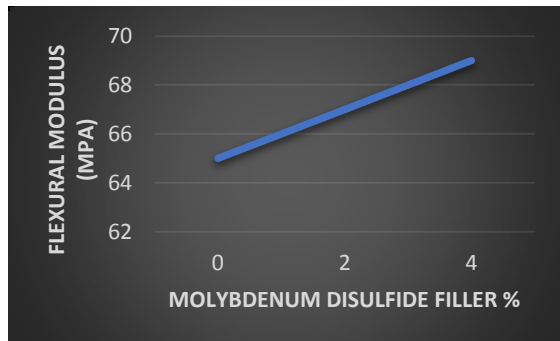Figure 4. Flexural Strength as a function of MoS<sub>2</sub> filler content.Figure 5. Flexural Modulus as a function of MoS<sub>2</sub> filler content.

### D. Hardness Properties

TABLE IV. HARDNESS TEST RESULTS

Sample no	GE-1	GE-2	GE-3
1	65	67	69
2	65	67	69
3	65	67	69

Hardness test was conducted according to ASTM D-2240 and the readings are tabulated in Table IV. Shore D Hardness number of glass fiber reinforced epoxy composites with and without MoS<sub>2</sub> filler were arrived at and average results are plotted as shown in Fig.6. Figure shows the linear increase in the hardness as the percentage of MoS<sub>2</sub> content increases, although the

magnitude increase in hardness with MoS<sub>2</sub> filler content is not substantial.

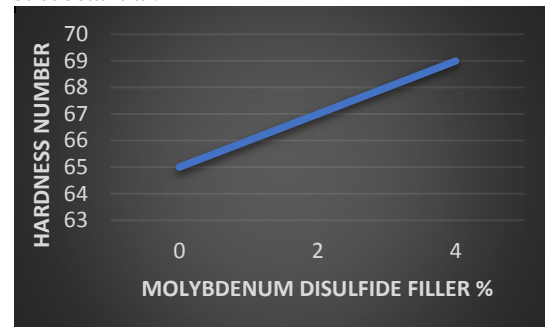


Figure 6. Hardness number as a function of Molybdenum disulfide filler content.

### E. Three Body Abrasive Wear Tests

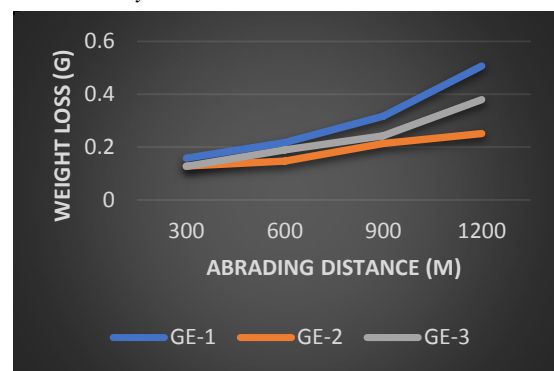


Figure 7. Fig 7. Weight loss Vs Abrading Distance

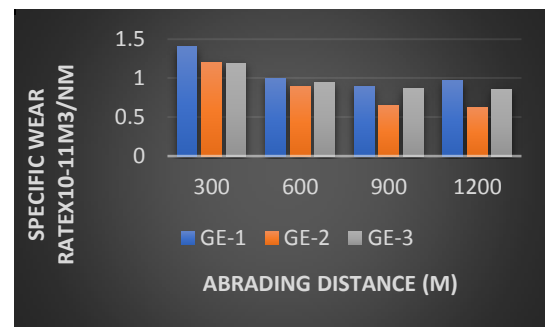


Figure 8. Specific Wear rate Vs Abrading Distance.

Fig. 7 show the weight loss in grams as a function of sliding distance for G-E composites with and without MoS<sub>2</sub> filler. It is observed that weight loss is increasing with increased abrading distance and amount of wear has been decreased with increase in MoS<sub>2</sub> filler content.

The addition of filler has altered the wear behaviour characteristics of composites and addition of filler has resulted in better wear resistance. From the graph it is clear that glass fiber reinforced epoxy composites with 2% MoS<sub>2</sub> filler showed the best wear behaviour than G-E composite without and with 4% MoS<sub>2</sub> filler.

Fig. 8 shows specific wear rate as a function of abrading distance for G-E composites with and without filler. These figures indicate that the specific wear rate generally dropped with increased abrading distance. G-E composite without filler showed maximum specific wear

rate at an abrading distance of 300m, whereas G-E composite with 2% filler showed the least specific wear rate.

Also it can be observed that the specific wear rate for G-E composites without filler and with 4% filler didn't show any fixed trend of variation with increased abrading distance, whereas specific wear rate for G-E composite with 2% filler marginally decreased with increased abrading distance for all the loads suggesting that 2% MoS<sub>2</sub> filled G-E composite showed stable wear characteristics as compared to other two.

#### F. Air Jet Erosion Test

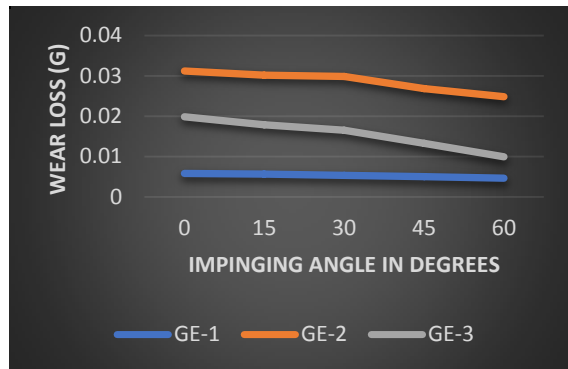


Figure 9. Weight loss Vs Impinging angle.

Fig.9 shows the erosive wear loss as a function of impinging angle. It is observed that erosive wear decreased with increased impinging angle. G-E composite with 2%MoS<sub>2</sub> additive resulted in lesser erosive wear compared with the other two. Also no significant variation of wear loss was observed. This shows that this composite with 2% MoS<sub>2</sub> filler showed stable wear properties even under ageing conditions.

#### IV. RESULTS

Glass fiber reinforced epoxy composite with 4% MoS<sub>2</sub> filler content showed the maximum tensile strength and elongation, whereas maximum flexural strength and modulus was obtained for G-E Composites with 2% MoS<sub>2</sub> filler. An increase in hardness was observed with increased percentage of MoS<sub>2</sub> filler in the composite.

Abrasive wear of glass fiber reinforced epoxy composite was strongly dependant on the test parameters such as load and sliding distance. Comparative wear performance of different composites showed increased weight loss and decreased specific wear rate with increased load and abrading distance. MoS<sub>2</sub> filler provided better abrasion resistance to composite as compared to unfilled ones. Also wear rate decreased with increased filler content. Best abrasive wear characteristics were obtained for the G-E composite with 2% MoS<sub>2</sub> filler.

Weight loss of G-E composite during abrasion test was strongly dependant on the test parameter namely impinging angle. Comparative erosive wear performance of all the composites showed that wear loss decreased with increased impinging angle. G-E composites with

filler showed better erosion resistance. Best erosive wear performance was seen for G-E composite with 2% MoS<sub>2</sub> filler.

#### REFERENCES

- [1] G. J. Aurrekoetxea, M. Sarrionandia and X. Gómez, "Effects of microstructure on wear behaviour of wood reinforced polypropylene composite," *Wear*, vol. 265, no. 5-6, August 25 2008, pp. 606-611.
- [2] A. K. Rout, A. Satapathy "Study on mechanical and tribo-performance of rice-husk filled glass-epoxy hybrid composites," *Materials and Design*, vol. 41, pp. 131-141, 2012.
- [3] B. Suresha, K. S. Kumar, S. Seetharamu, P. SampathKumaran, "Friction and dry sliding wear behavior of carbon and glass fabric reinforced vinyl ester composites," *Tribology International*, vol. 43, pp. 602-609, 2010.
- [4] A. Satapathy, A. K. Jha, S. Mantry, S. K. Singh, A. Patnaik, "Processing and characterization of jute-epoxy composites reinforced with SiC derived from rice husk," *J ReinfPlast Compos*, 2010.
- [5] N. Mohan, S. Natarajan, S. P. KumareshBabu, "Abrasive wear behaviour of hard powders filled glass fabric-epoxy hybrid composites," *Materials and Design*, vol. 32, pp. 1704-1709, 2011.
- [6] Tensile Properties of Fiber-resin Composites ASTM D 3039-76. American
- [7] J. Stabik and A. Dybowska, "Electrical and tribological properties of gradient epoxy-graphite composites," *JAMME*, vol. 27, March 2008, pp. 39-42
- [8] J. K. Lancaster, "The effect of carbon fiber reinforcement on friction and wear of polymers," *J. Appl. Phy.*, vol. 1, pp. 549-555, 1968.
- [9] V. K. Srivastava and A. G. Pawar, "Solid particle erosion of glass fiber reinforced flash filled epoxy resin composites," *Composite Science and Technology*, 2006, pp. 3021-3028
- [10] N. Mohan, S. Natarajan, S. P. KumareshBabu, Siddaramaiah, "Investigation on two-body abrasive wear behavior of silicon carbide filled glass fabric-epoxy composites," *JMMCE*, vol. 9/3, pp. 231-246, 2010.
- [11] B. Suresha, G. Chandramohan, N. M. Renukappa, Siddaramaiah, "Mechanical and tribological properties of glass-epoxy composites with and without graphite particulate filler," *Material Science Engg.*, vol. 103, pp. 2472-2480, 2007.
- [12] B Suresha, "Experimental studies using SiC instead of graphite as the filler material in E-glass reinforced thermoset composites," *JMMCE*, vol. 26/6, pp. 565-578, 2009.



**Mr. Vijay B R.** born on 28/03/1985 and brought up in Mysore, Karnataka State, India. He is pursuing his Doctor of Philosophy in Mechanical Engineering, Visvesvaraya Technological University, Belagavi under the valuable guidance of Dr. Srikantappa A S. He obtained his Master of Science in Engineering by Research at National Institute of Engineering Mysore. He obtained his Bachelor of Engineering from Vidya Vikas Institute of Engineering & Technology, Mysuru, Visvesvaraya Technological University, Belagavi. Mr. Vijay B R is having 8 years of teaching experience and 3 years of industrial experience. He is currently working as COO of IntraLabs India Technology Private Limited, Bengaluru Karnataka State, India. He has taught many subjects include Mechanics of Materials, Design of Machine elements, Control Engineering, Computer Aided Engineering Drawing, Computer Aided machine Drawing, Finite Element Method, Operations Research etc. His areas of interest are Material science and Design. Mr. Vijay B R has published more than 5 International journal papers and more than 8 national conference papers.



**Dr. Srikantappa A S** born on 08/12/1968 and brought up in Arakere Village, Mandya District, Karnataka State, India. Doctor of Philosophy in Mechanical Engineering from Kirupananda Variyar Engineering College Salem Tamil Nadu State India. He completed his Master of Technology in Production Engineering Systems Technology from National Institute of Engineering Mysore Karnataka State India. He completed his Bachelor of Engineering in

Industrial Production Engineering from P.E.S College of Engineering Mandya Karnataka State India. He obtained his LLB from H. Hombegowda Memorial Law College Mandya Karnataka State India. Dr. Srikantappa A S Served as Member of Local Inspection Committee for VTU Affiliation. He served as Research Supervisor at Visvesvaraya Technological University Research Resource Centre Belagavi Karnataka India. He is having a 8 years of experience as Principal and currently serving as Principal at Cauv